

Article

Potential Role of Exciton in Photocatalysis

Andrey A Lisachenko * and Boris V Novikov

Department of Physics, Saint-Petersburg State University, Ul'yanovskaya str., 1, Saint-Petersburg 198504, Russia; bono1933@mail.ru (B.V.N.)

* Corresponding author. E-mail: Andalis0505@gmail.com

Received: 29 May 2023; Accepted: 23 August 2023; Available online: 31 August 2023

ABSTRACT: This article commemorates the outstanding Russian scientists E.F. Gross and A.N. Terenin. It revisits their successors' efforts to develop Terenin's idea of using excitons, discovered by Gross, for photocatalytic redox reactions on wide-gap semiconductors. Terenin proposed ZnO as the subject of study. To explore the possibility of replacing photogenerated electrons and holes in a redox reaction by an exciton being a quasi-neutral particle, the test reaction of the photoactivated oxygen isotope exchange (POIE) was studied. It was found that many years of initial unsuccessful attempts were due to the fact that the exciton energy is spent on luminescence. In our experiments, the excitons decayed non-radiatively, and the long-lived electron-donor F-type and hole V-type active centers were formed by creating the 2D surface nanostructure $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$. These centers allowed to obtain the reaction efficiency 5–8 times higher than with the interband transitions. Thus, the developed 2D surface nanostructure $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$ resolved the problem of using an exciton in photocatalysis and demonstrated the perspective of this nanostructure as an efficient photocatalyst.

Keywords: Photocatalysis; ZnO; Exciton; Photoactivated oxygen isotope exchange (POIE); Redox reactions



© 2023 by the authors; licensee SCIEPublish, SCISCAN co. Ltd. This article is an open access article distributed under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

1. Introduction

In 1952, E.F. Gross discovered the neutral quasiparticle exciton in a semiconductor crystal [1]. His colleague A.N. Terenin pointed out the advantages of using an exciton instead of traditional free carriers for photo-activation of catalytic redox reactions on semiconductor crystals. He suggested to test ZnO being a leading photocatalyst [2]. Gross and Novikov experimentally established for the first time that in semiconductor crystals an exciton interacts with the surface and local centers [3], thus participating in electronic processes on the surface.

ZnO is the most active (along with TiO_2) photocatalyst for redox reactions due to the features of the electronic structure of ZnO such as a large band gap (3.37 eV at 300 K), an electron affinity of ~ 4.0 eV, and a high carrier mobility ($200 \text{ cm}^2/\text{V}\cdot\text{s}$ at 300 K). In the UV irradiated ZnO, the e^-/h^+ pairs have one of the highest redox potentials among the photocatalysts and can be used in photochemical cells for water decomposition and decontamination of the environment from a wide range of organic and inorganic pollutants. The main obstacle in achieving a high photoinduced efficiency upon UV activation is the e^-/h^+ pair decay when moving from bulk to surface centers of photocatalysis because of the recombination with each other and with the recombination centers. A.N. Terenin pointed out that these losses can be avoided by using excitons to transfer the excitation energy [2]. The uniquely high exciton binding energy in ZnO of 60 meV ensures the stability of the e^-/h^+ pairs during their transfer at room temperature ($kT = 27 \text{ meV}$). However, this idea has taken decades of experimental research to be put into practice. In this paper, we present the results of these studies.

2. Initial Researches

In the initial experiments, the successors of A.N. Terenin investigated the effect of ZnO illumination on the test reaction photoactivated oxygen isotope exchange (POIE) widely used for testing photocatalysts elaborated mainly on the basis of TiO_2 oxide [4–8]. The activity of excitons in photocatalysis on ZnO was experimentally confirmed in 1990 [6]. The exciton excitation maximum for the POIE reaction on ZnO has been discovered. However, the magnitude of the effect turned out to be lower than that under the excitation in the region of interband transitions. It was found out that the main intensity losses were caused by a radiative decay of the exciton. The exciton decays on the surface radiatively, and the internal energy dissipates in the form of the exciton photoluminescence (PL) with an efficiency of up to 100%. The delay in confirming the activity of excitons in photocatalysis was due to this radiative decay.

3. Fundamental Researches

In 2010s, the joint work of the successors of E.F. Gross and A.N. Terenin started. The planned program included 3 points:

1. Suppress the radiative decay of excitons on the surface.
2. Use the energy of nonradiative decay of an exciton to generate the long-lived electron-donor F-type and hole V-type surface centers.
3. Ensure the interaction of the generated centers with the molecules of the gas phase, resulting in the POIE reaction.

After an extended research, a way to suppress the channel of the radiative exciton decay was found. It was shown that the surface PL of ZnO can be suppressed by a specific change in oxygen concentration in the surface layer of the crystal and in the adsorbed layer [9]. At the first stage, photo-desorption of adsorbed oxygen and dosed photo-reduction of the ZnO surface layer were carried out in Ultra High Vacuum (UHV). The amount of photo-desorbed oxygen was controlled by a mass spectrometer (MS) observing a decrease in the intensity of the subsequent thermo-desorption spectrum (TDS) of the adsorbed oxygen. The excess of photo-desorbed oxygen over the TDS can naturally be associated with the photo-desorption of surface structural oxygen. To confirm this, a 2D structure “core-shell” ZnO/ZnO_{1-x} was suggested to be formed. The value of “x” was determined by measuring the amount of released oxygen and the size of the illuminated surface [9,10]. A photo-processing caused changes in the electrical parameters of the sample (see Figure 1). According to measurements with an original ultra-violet photoelectron spectrometer (UPS, 8.43 eV) [9,11] from the outer side of the surface, the value of the dipole component $\Delta\delta$ of the thermoelectric work function ϕ_T dropped to zero. On the inner side of the surface, due to the recharging of “fast” surface states, the value of the band bending of the initial “oxidized” sample V_s decreased, and a potential barrier was created separating the surface states from the volume. The result of such processing was not a suppression, but an increase in the PL intensity compared to the original sample. The mechanism of the process was discussed in [9].

The next step in the formation of the 2D structure was the adsorption of O⁻ radicals onto the surface. As a result, the barrier $\Delta\delta$ is restored on the outer side, forming a quantum well together with the inner barrier. Here ZnO/ZnO_{1-x} is a 2D structure “core-shell” and O⁻ is the adsorbed atomic oxygen capturing an electron, thus forming a locking barrier over the “core-shell” structure. A high field strength inside the well leads to a dissociative polarization of the exciton, causing its nonradiative decay. As a result, a “dead zone” for the exciton is created in the surface subatomic region of ZnO_{1-x}/O⁻. The exciton decays, and the free electron and hole are localized on F- and V-type defects of the ZnO_{1-x} surface layer.

The 2D structure ZnO/ZnO_{1-x}/O⁻ was formed using ZnO high purity (99.99%) powder “OSCh 12-2” with the wurtzite structure, consisting of 20–500 nm nanocrystallites [9]. The samples were characterized using optical and photo-luminescence spectroscopy (PL). Thermo-stimulated luminescence (TSL) in ultraviolet (UV) and visible (VIS) light, scanning electron microscopy (SEM), ultraviolet photoelectron spectroscopy (UPS) (21.4, 8.43 eV), and X-ray Diffraction (XRD). UPS (8.43 eV) allowed us to determine *in situ* the ϕ_T of the sample and to separate the contributions of the dipole component δ from the band bending V_s . The 2D structure includes a sub-monolayer potential electron shell bounded from inside by the electron potential at the surface states and from outside by a potential barrier created by the adsorbed oxygen O⁻.

We have studied this composite with original UPS (8.43 eV) and MS methods [9,10,11]. The energy diagram of its 2D structure is shown in Figure 1. In such a structure the exciton does not emit light, but decays into a pair $e^- + h^+$ which fills the vacancies appearing on the photo-restored surface.

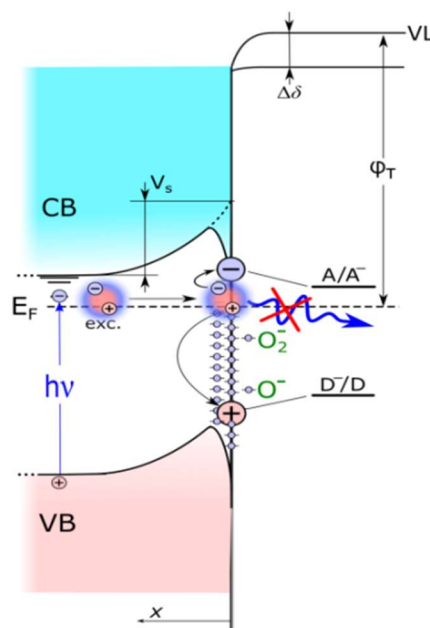


Figure 1. Radiationless decay of exciton into a pair of long-lived centers in the 2D structure ZnO/ZnO_{1-x}/O⁻. VB—valence band, CB—conduction band, E_F—Fermi level, VL—vacuum levels before and after oxygen desorption, $\Delta\delta$ —dipole component, ϕ_T —thermoelectric work function, V_s —band bending of the original “oxidized” sample, A/A⁻, D/D⁺—acceptor and donor reagent levels.

The second point of the research program was to find out the fate of the electron and hole formed during the decay of the exciton. It is natural to expect the possibility of their localization on F- and V-type defects of the ZnO_{1-x} surface layer. To test this possibility, we studied TSL after illuminating the structure at the exciton absorption line. A TSL with a maximum at 475 K was detected (see Figure 2), comprising spectral regions typical for F- and V-type centers [10]. The energy of the absorbed light was retained for 8×10^3 s, which is typical for F- and V-type centers. It is these centers that sensitize the photocatalytic activity of reduced ZnO_{1-x} samples [12]. Thus, it has been shown that when the $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$ structure is illuminated in the region of exciton resonance, the active centers are formed on its surface providing the photocatalytic activity of ZnO_{1-x} .

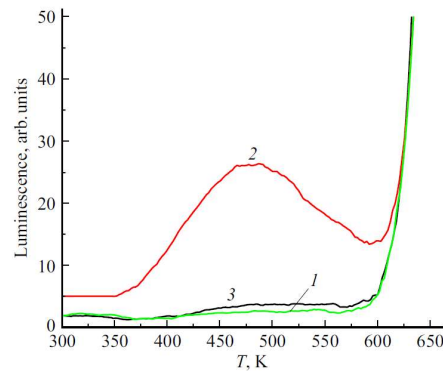


Figure 2. Thermally stimulated luminescence (TSL) of F-type and V-type centers in $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$ illuminated by a monochromatic light. Curve 1: $\lambda = 365$ nm, Curve 2: $\lambda = 385$ nm. Curve 3: $\lambda = 385$ nm, the sample preliminarily kept in an oxygen atmosphere at 10^{-1} Torr.

3.1. Thermal Desorption Spectra (TDS) of O_2

Finally, the third point of the program was to check whether the centers active on the ZnO_{1-x} surface will also be active on the surface of $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$. This can be verified by analyzing the interaction of active centers with oxygen molecules from the gas phase, since the criterion for the activity of a photo-catalyst is its activity in the POIE reaction. To characterize the interaction of gas molecules with a photo-activated surface, we analyzed the TDS of oxygen adsorbed onto $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$, which was previously exposed to the exciton absorption line. These TDS coincided with the previously obtained TDS of oxygen, adsorbed on the pre-illuminated ZnO_{1-x} photo-catalyst, and they had 3 maxima at $E_{\text{des}} = 0.6, 1.1$ and 1.3 eV. The first maximum is attributed to the desorption of O_2 from the O_2^- form adsorbed on F-type electron-donor centers, the second one is attributed to the desorption of O_2 from the O_3^- complex adsorbed on V-type hole centers, the third maximum is the result of the associative desorption of atomic oxygen.

Thus, it can be expected that the 2D structure $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$ makes it possible to use the exciton energy to carry out the POIE reaction.

3.2. Experimental Study of the Photocatalytic Reaction of POIE on a 2D Structure $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$

In the experiments, two versions of the experimental flow-through reactor were used. The first one was made of optical quartz [13]. The stainless steel chamber of the second reactor [11] had two sapphire windows, one for UPS excitation light (146.6 nm, 8.43 eV) and another for UV-VIS photoexcitation of the sample and for thermo-PL detection. The continuous analysis of the gas composition above the sample was carried out on the first reactor at the pressures of 10^{-1} – 10^{-4} Torr, while on the second one at 10^{-5} – 10^{-8} Torr. The amount and the composition of the adsorbed layer was analyzed by the TDS method. A heater and a thermocouple allowed one to adjust and to control the sample temperature in the 77 – 750 K range.

The diagram of “flow-through” regime is presented in Figure 3.

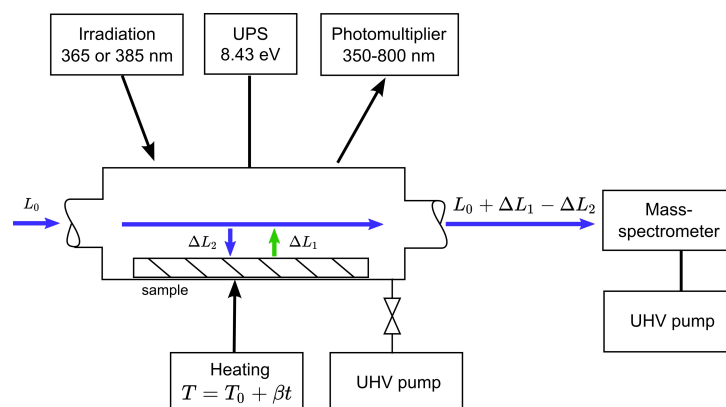


Figure 3. Block diagram of the sample chamber.

The flow of O_2 gas L_0 , injected into the chamber, passes over the sample, increasing by L_1 due to the desorption from the sample and decreasing by L_2 due to the adsorption on the sample, and the resulting flow $L_0 + L_1 - L_2$ enters the MS. The adsorption and desorption values measured as the deviations in the amplitudes of the MS signals from the stationary values L_0 correspond to the reaction rates (a differential measurement mode).

The electrostatic electron energy analyzer of original design [11] is extremely compact and does not interfere with chemical measurements. The 99.99% chemical purity mixtures of isotopes $^{18}O_2$ and $^{16}O_2$ were used, while the ZnO sample had a natural isotopic composition. The POIE has been chosen as a test reaction which was successfully used [4–8] to study the mechanism of photo-activation of heterogeneous reactions. Further details of the experimental setup and of the results processing are given in Ref. [13].

For the interband excitation the 365 nm line was chosen. It was obtained from the DRSh-500 high-pressure Hg lamp using the LOMO glass color filters USF-6 and BS-7 and additionally accentuated by the KSVU-1 monochromator. For the exciton excitation, a RF-UVXC35LN-UD (Refond) UV LED was used. According to the datasheet, it should have a peak at 375–380 nm, but we measured it at 388 nm (Figure 4). In the same figure, the light-emitting diode radiation spectrum multiplied by the absorption spectrum is presented. One can see that the spectrum of the absorbed radiation is situated inside the area of the exciton resonant excitation (Figure 4). In both cases, the radiation power absorbed by the sample was (10 ± 2) mW.

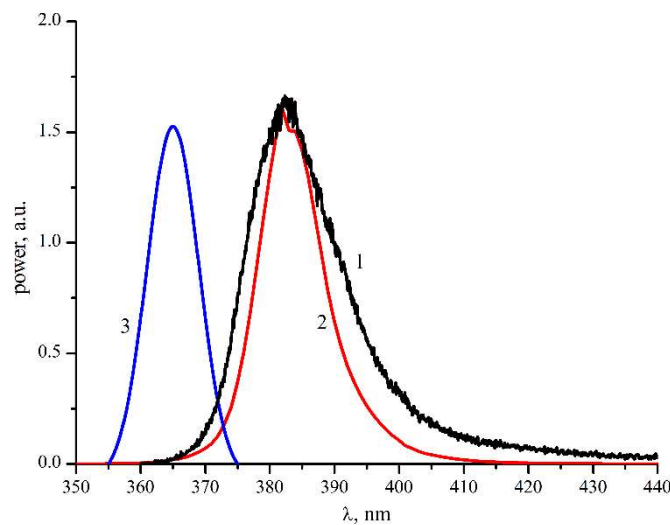


Figure 4. 1—spectra of the exciton resonant excitation at RT; 2—spectrum of the sample illumination by LED RF-UVXC35LN-UD (Refond), taking into account the absorption of the sample; 3—365 nm emission of DRSh-500 accentuated by the monochromator KSVU-1.

In our experiments we monitored the current concentrations (partial pressures) of $^{16}O_2$, $^{16}O^{18}O$ and $^{18}O_2$ molecules in the gas phase as well as the total pressure above the illuminated sample. The obtained results presented in Figure 5 clearly show the presence of the photo-activation effect in the O_2 -ZnO/ZnO $_{1-x}$ /O $^-$ system. For the quantitative analysis of the mechanism of the process, we have examined its individual stages.

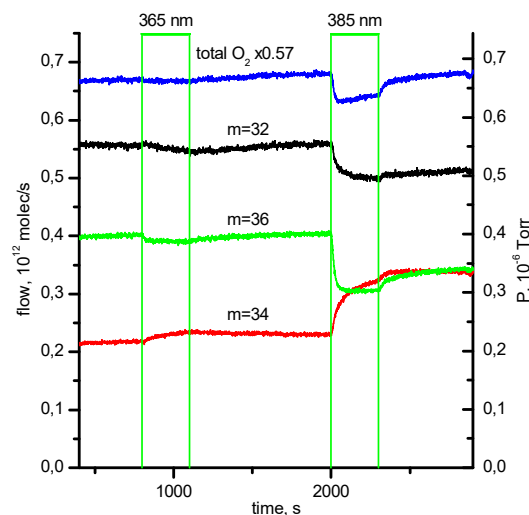


Figure 5. Effect of interband and exciton irradiation of the sample on the isotopic composition of the gas phase over the sample. The absorbed irradiation power for $\lambda = 365$ nm and $\lambda = 385$ nm is (10 ± 2) mW, $P = 1.2 \times 10^{-6}$ Torr.

3.3. POIE Kinetics

A mixture of oxygen atoms containing the ^{16}O and ^{18}O isotopes can be fully characterized by three parameters: P , α , and Y , where P represents the total pressure, α is the percentage of ^{18}O atoms among all O atoms in the gas phase, and $Y = 2\alpha(1 - \alpha) - C_{34}$ represents the deviation of the mixture from the equilibrium with respect to the homo-molecular exchange reaction $^{16}\text{O}_2 + ^{18}\text{O}_2 \leftrightarrow ^{16}\text{O}^{18}\text{O}$. Here C_{32} , C_{34} , and C_{36} represent the current normalized concentrations of the molecules $^{16}\text{O}_2$, $^{16}\text{O}^{18}\text{O}$, and $^{18}\text{O}_2$ in the gas phase, respectively. $Y = 0$ corresponds to the equilibrium mixture; if a mixture undergoing the homo-exchange has an initial non-zero Y , it will tend to zero with time. The rate of photoactivated isotope equilibration in the gas phase (homo-exchange POIEq) is denoted as R_q , expressed in molecules per second. In a closed volume at the pressures $P < 0.1$ Torr, the POIEq process balances the mixture too quickly, thus we worked in a flow-through mode, with a continuous influx of fresh unbalanced mixture. This allowed us to continuously measure the rate of homo-exchange for an arbitrarily long time.

The hetero-exchange (POIEx) is the exchange between the isotope-enriched gas-phase molecules and the surface oxygen molecules or atoms (lattice or preadsorbed) of the sample (having a natural isotopic composition [^{18}O] = 0.25%). The rate of this process is denoted as R_x and is expressed in atoms per second.

3.4. Modeling of the Kinetics of POIE $\text{O}_2 \rightleftharpoons \text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$

The Figure 6 reflects all the stages of the process described in the article: photogeneration of an exciton \rightarrow its diffusion to the surface \rightarrow decay in the “dead zone” of a 2D surface structure into an electron and a hole \rightarrow activation of F- and V-type centers by e^- and h^+ \rightarrow interaction of activated centers with molecules of the gas phase \rightarrow desorption of isotope-exchanged molecules into the gas phase.

We propose a four-channels model to describe the interaction between the O_2 gas and $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$ during the POIE in a flow-through reactor: (1) O_2 photo-adsorption, (2) O_2 photo-desorption, (3) isotope exchange in the gas phase (homo-exchange), and (4) isotope exchange at the surface $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$ – gas (hetero-exchange). The corresponding equations have been derived and the experimental data has been analyzed [14].

The dependences of the rates of these processes were determined from the measured kinetic parameters of the outflow. The theoretical model was proposed to describe the decomposition of the interaction of O_2 gas with $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$ through these channels.

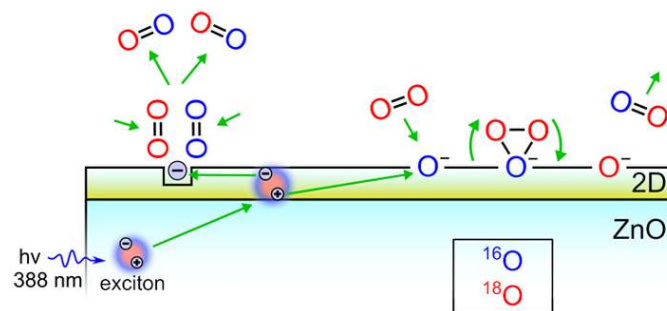


Figure 6. The radiative decay of an exciton is excluded by a 2D structure $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$, in which the exciton decays nonradiatively into a pair of long-lived (up to 8×10^3 s) electron and hole local states, on which a chemical reaction take place.

The equation for this process can be written in a vector-like form:

$$\frac{d\vec{N}}{dt} = \vec{F}_{in} - \vec{F}_{out} - R_{PA} \frac{\vec{N}}{|\vec{N}|} + \vec{R}_{PD} + R_x \cdot \left(-\frac{\vec{N}}{|\vec{N}|} + \begin{pmatrix} 1 \\ 0 \\ 0 \end{pmatrix} \right) + R_q \cdot \left(-\frac{\vec{N}}{|\vec{N}|} + \begin{pmatrix} \alpha^2 \\ 2\alpha\tilde{\alpha} \\ \alpha^2 \end{pmatrix} \right) \quad (1)$$

The notations in this equation follow:

The components of the vector \vec{N} are the numbers of O_2 isotope molecules in the reactor with masses 32, 34 and 36. The module of this vector is defined as the sum of its components, $N = |\vec{N}| = N_{32} + N_{34} + N_{36}$. The α value is defined by $\alpha = \frac{N_{36} + 0.5 \cdot N_{34}}{|\vec{N}|}$ and means the fraction of the ^{18}O isotope in the gas phase, while $\tilde{\alpha} \equiv (1 - \alpha)$ is the fraction of ^{16}O . R_x is the rate of homo-exchange, measured in [molec/s], and R_q is the rate of hetero-exchange, measured in [atoms/s].

$\vec{F}_{out} = \frac{\vec{N}}{\tau_{pump}}$ is the outflow [molec/s], i.e., number of the molecules captured by MS in the time τ_{pump} (reactor pumpdown time constant) and \vec{F}_{in} is the inflow [molec/s] set in the experiment. The values \vec{N} , R_x , R_q , \vec{F}_{out} , \vec{F}_{in} , R_{PA} depend on time.

The first two terms on the right side of (1), $\vec{F}_{in} - \vec{F}_{out}$, correspond to the flow regime. The third term $-R_{PA} \frac{\vec{N}}{|\vec{N}|}$ is “photo-adsorption”. The fourth one \vec{R}_{PD} is “photo-desorption”. The fifth one is “hetero-molecular exchange”, and the last one is “homo-molecular exchange”. The equation is a differential non-linear one, however the value under the differential is known, and

the equation can be transformed into an algebraic one. In the experiments performed, photo-desorption was not observed, therefore, we consider it to be equal to zero.

The notation

$$\vec{A} = \frac{d\vec{N}}{dt} - \vec{F}_{in} + \vec{F}_{out} + R_{PA} \frac{\vec{N}}{|\vec{N}|}$$

allows to rewrite (1) as

$$\vec{A} = R_x \cdot \left(-\frac{\vec{N}}{|\vec{N}|} + \begin{pmatrix} 1 \\ 0 \\ 0 \end{pmatrix} \right) + R_q \cdot \left(-\frac{\vec{N}}{|\vec{N}|} + \begin{pmatrix} \alpha^2 \\ 2\alpha\bar{\alpha} \\ \alpha^2 \end{pmatrix} \right).$$

In order to compare the theory to the experimental results we denote $R_{x_at} = \frac{A_{32} - A_{36}}{\alpha}$ and $R_q = \frac{A_{34} + R_{x_at} \cdot \alpha \bar{\alpha}}{\gamma} - \frac{1}{2} R_{x_at}$.

The results obtained for R_q and R_x are shown in Figure 7.

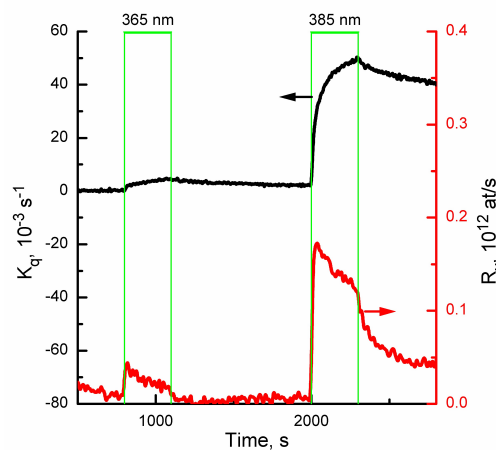


Figure 7. Rates of $k_q = R_q/N$ and R_x over $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$ under irradiation in the region of interband absorption at $\lambda = 365$ nm and exciton absorption at $\lambda_{\text{max}} = 385$ nm. The incident photon fluxes were 1.8×10^{16} ($\pm 20\%$) quanta per second, $P = 1.2 \times 10^{-6}$ Torr. For POIE test reaction the irradiating in the exciton absorption band is about 5–8 times more effective than in the interband absorption.

Thus, the example of the POIE used as a model for redox reactions shows that the efficiency of the 2D structure $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$ activated in the region of the resonant exciton excitation is ~5–8 times higher than in the region of the interband absorption [13].

4. Conclusions

In summary, the prediction of A.N. Terenin is confirmed: the exciton discovered by E.F. Gross, being a neutral quasi-particle, can work in redox photocatalysis more efficiently than photo-generated charged particles: electrons and holes. For the first time, the 2D structure $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$ was developed, in which the exciton energy is spent not on luminescence, but on the generation of long-lived (up to 8×10^3 s) F- and V-type centers that activate the photocatalytic redox reaction. The efficiency of the photocatalyst in the POIE reaction at the exciton excitation is ~5–8 times higher than that under interband absorption.

Thus, the 2D structure $\text{ZnO}/\text{ZnO}_{1-x}/\text{O}^-$, when activated in the region of exciton absorption, is expected to be a highly efficient photocatalyst.

Acknowledgments

This work was financially supported by RFBR under Grant 18-03-00754. The research was supported by “Nanocomposite”, “Physical Methods of Surface Investigation”, “X-ray Diffraction Centre”, and “Nanophotonics” centres of St. Petersburg State University. The authors are grateful to their colleagues: Titov, V.V., Tklich, V.S., Mikhaylov, R.V., Akopyan, I.K., Labzowskaya, M.E. for performing experiments and discussing the results. B.V.N. acknowledges the support of St. Petersburg State University through the Grant ID 94033852.

Author Contributions

Conceptualization; Methodology; Validation; Formal Analysis; Investigation; Resources; Writing-Original Draft Preparation; Supervision; Funding Acquisition.

The contribution of each of the co-authors for each item was 50%.

Funding

This research received no external funding.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

References

1. Gross EF, Karryev NA. Opticheskii spektr eksitona. *Doklady Akademii Nauk USSR* **1952**, *84*, 471–474 (In Russian).
2. Terenin AN. Release of adsorbed gases from metals and semiconductors and their adsorption under the action of light. *Probl. Kinet. Catal.* **1955**, *8*, 17 (In Russian).
3. Gross EF, Novikov BV. The Fine Structure of the Spectral Curves of Photoconductivity. *J. Phys. Chem. Sol.* **1961**, *22*, 87–100.
4. Formenti M, Courbon H, Juillet F, Lissatchenko A, Martin JR, Meriaudeau P, et al. Photointeraction between Oxygen and Nonporous Particles of Anatase. *J. Vac. Sci. Techn.* **1972**, *9*, 947–952.
5. Courbon H, Formenti M, Pichat P. Study of Oxygen Isotopic Exchange over Ultraviolet Irradiated Anatase Samples and Comparison with the Photooxidation of Isobutane into Acetone. *J. Phys. Chem.* **1977**, *81*, 550–554.
6. Tkalich VS, Lisachenko AA. The Mechanism of Photoactivation of Isotopic Exchange of Oxygen Adsorbed on ZnO. *Sov. J. Chem. Phys.* **1990**, *6*, 1264.
7. Pichat P, Courbon H, Enriquez R, Tan TTY, Amal R. Light-Induced Isotopic Exchange between O₂ and Semiconductor Oxides, a Characterization Method That Deserves Not to Be Overlooked. *Res. Chem. Intermed.* **2007**, *33*, 239–250.
8. Titov VV, Mikhaylov RV, Lisachenko AA. Spectral Features of Photostimulated Oxygen Isotope Exchange and NO Adsorption on “Self-Sensitized” TiO_{2-x}/TiO₂ in UV–Vis Region. *J. Phys. Chem. C* **2014**, *118*, 21986–21994.
9. Titov VV, Lisachenko AA, Akopyan IK, Labzovskaya ME, Novikov BV. On the Nature of the Effect of Adsorbed Oxygen on the Excitonic Photoluminescence of ZnO. *J. Lumin.* **2018**, *195*, 153–158.
10. Titov VV, Lisachenko AA, Akopyan IK, Labzovskaya ME, Novikov BV. Long-Lived Photocatalysis Centers Created in ZnO via Resonant Exciton Excitation. *Phys. Solid State* **2019**, *61*, 2134–2138.
11. Aprelev A, Lisachenko A, Laiho R, Pavlov A, Pavlova Y. UV ($h\nu = 8.43$ eV) photoelectron spectroscopy of porous silicon near Fermi level. *Thin Solid Films* **1997**, *297*, 142–144.
12. Blashkov, Ilya V., Basov, Lev L. and Lisachenko, Andrey A. Photocatalytic Reaction $\text{NO} + \text{CO} + h\nu \rightarrow \text{CO}_2 + 1/2\text{N}_2$ Activated on ZnO_{1-x} in the UV–Vis Region. *J. Phys. Chem. C* **2017**, *121*, 28364–28372.
13. Titov VV, Lisachenko AA, Labzovskaya ME, Akopyan IK, Novikov BV. Exciton Channel of Photoactivation for Redox Reactions on the Surface of 2D ZnO Nanostructures. *J. Phys. Chem. C* **2019**, *123*, 27399–27405.
14. Titov VV, Lisachenko AA. Modeling of the Kinetics of Photoactivated Isotope Exchange $\text{O}_2 \rightleftharpoons \text{ZnO}$ in a Flow-Through Reactor. *Kinet. Catal.* **2021**, *62*, 900–905 (Russian Text: *Kinetika i Kataliz* **2021**, *62*, 29–37).